



Impurity-induced polar Kerr effect in a chiral p -wave superconductor

Jun Goryo*

Department of Physics, Nagoya University, Furo-cho, Nagoya 464-8602, Japan

(Received 21 June 2008; revised manuscript received 15 July 2008; published 6 August 2008)

We discuss the polar Kerr effect in a chiral p -wave (p_x+ip_y -wave) superconductor. It is found that the off-diagonal component of a current-current correlation function is induced by impurity scattering in the chiral p -wave condensate, and a nonzero Hall conductivity is obtained using the Kubo formula. We estimate the Kerr rotation angle by using this impurity-induced Hall conductivity and compare it with experimental results [J. Xia *et al.*, Phys. Rev. Lett. **97**, 167002 (2006)].

DOI: 10.1103/PhysRevB.78.060501

PACS number(s): 74.25.Nf, 74.20.Rp, 74.25.Gz, 74.70.Pq

Recently, the quasi-two-dimensional (quasi-2D) superconductor Sr_2RuO_4 with $T_c=1.5$ K has attracted considerable attention and it has been investigated extensively.¹ It is plausible that the order parameter in Sr_2RuO_4 has the spin triplet $p_x \pm ip_y$ -wave symmetry. One of the fascinating properties of this state is the spontaneous breaking of parity in a two-dimensional (2D) sense ($p_x \rightarrow p_x$ and $p_y \rightarrow -p_y$) and in a time-reversal symmetry due to the presence of nonzero chirality characterized by $l_z = \pm 1$, where l_z is the z component of the relative orbital angular momentum of the Cooper pair.

The polar Kerr effect (PKE), in which the direction of polarization of reflected linearly polarized light is rotated, has been known as an effective tool for understanding ferromagnetism.² Because of the analogy between ferromagnetic order—for instance, with $s_z=1$ and chiral pair condensation with $l_z=1$ —it is naively expected that the PKE is induced in the chiral p -wave state at zero field. In fact, the PKE has been observed in the superconducting state of Sr_2RuO_4 .³ Up-to-date theoretical reports on the PKE in the chiral p -wave state are given in Refs. 4 and 5, in which interesting mechanisms have been proposed by the field theoretical approach; however, obtained results of the Kerr rotation angle are considerably smaller than the experimental results.

Therefore, it is crucial to elucidate the fundamental nature of the PKE in the chiral p -wave superconductor. We will show that a Kerr rotation angle comparable to that obtained experimentally is obtained by taking into account nonmagnetic and short-ranged impurity scatterings of quasiparticles in a chiral p -wave condensate. It is also found that this impurity-induced PKE is suppressed or is zero for any superconducting state other than the chiral p -wave state.⁶ This result is contrary to the naive analogy with a ferromagnet, since the effect is not proportional to chirality analogous to magnetization but suppressed in higher chirality states with $l_z = \pm 2, \pm 3, \dots$. The natural unit $\hbar=c=k_B=1$ is used throughout this Rapid Communication.

We reviewed the phenomenology of the PKE in time-reversal symmetry-breaking superconducting systems, which is an extension of the argument for itinerant ferromagnetic systems.^{2,8} We also refer to the discussion of anyon superconductivity.⁹ Let us suppose that $z>0$ is empty, $z<0$ is filled by the superconductor, and incident light is linearly polarized and propagating along the z direction perpendicular to the superconducting plane with a wave vector $\mathbf{q} = -\hat{z}q_z$.

The Maxwell equations inside the material are $\hat{z}\nabla_z \times \mathbf{E} = -\partial \mathbf{B} / \partial t$ and $\hat{z}\nabla_z \times \mathbf{B} = \mathbf{j} + \partial \mathbf{E} / \partial t$. It is obvious that for manifestly gauge-invariant systems, current $j_i = \sum_{j=x,y} \sigma_{ij} E_j = -\sum_j \sigma_{ij} (\dot{A}_j + \partial \phi / \partial x_j)$ —where $i=x,y$, σ_{ij} is the conductivity tensor, and A_i and ϕ are the vector and scalar potentials, respectively. In superconductors,

$$j_i = - \sum_j \left[\sigma_{ij}^{(v)} \dot{A}_j + \sigma_{ij}^{(s)} \frac{\partial \phi}{\partial x_j} \right], \quad (1)$$

and in general, $\sigma_{ij}^{(v)} \neq \sigma_{ij}^{(s)}$ because of the spontaneous breaking of the gauge symmetry.^{9,10} The scalar potential becomes redundant in this problem, and we select a $\phi=0$ gauge. In this gauge, the Maxwell equation inside the superconductor is

$$\{[\omega^2 - q_z^2 + i\omega\sigma_{xx}^{(v)}(\omega)]\delta_{ij} + i\omega\epsilon_{ij}\sigma_{xy}^{(v)}(\omega)\}A_{jq}(\omega) = 0.$$

Here, we suppose that the long-wavelength limit $\mathbf{q} \ll \xi^{-1}$, where ξ is the coherence length of the superconducting order parameter, and we omit the \mathbf{q} dependence of the conductivity tensor. It is clear that there are two propagating modes $q_z^\pm = \sqrt{\omega^2 + i\omega\sigma_{xx}^{(v)}(\omega) \pm \omega\sigma_{xy}^{(v)}(\omega)}$. In Ref. 9, the low-frequency limit $\omega \ll 2|\Delta|$ has been considered and only the static values $\sigma_{ij}^{(v)}(\omega=0)$ have been considered. However, this value is not suitable for the experimental situation in the ruthenate $\omega = 0.8$ eV $\gg 2|\Delta| \approx 10^{-4}$ eV.³ Following Ref. 8, we solve the Maxwell equation with an appropriate boundary condition at $z=0$ and obtain the Kerr rotation angle,

$$\theta_K = - \text{Im} \left[\frac{\omega(q_z^+ - q_z^-)}{\omega^2 - q_z^+ q_z^-} \right], \quad (2)$$

which would be applicable in a wide frequency region. The factor $(q_z^+ - q_z^-)$ indicates that $\sigma_{xy}^{(v)}(\omega)$ is crucial to the PKE.

Let us calculate $\sigma_{ij}^{(v)}(\omega)$, with $\omega \gg 2|\Delta|$ in the chiral p -wave state. We use a quasiparticle Hamiltonian with a cylindrical Fermi surface that models the dominant γ band in Sr_2RuO_4 .¹ The electromagnetic interaction and impurity scattering are also taken into account. In the Nambu representation $\Psi_{\mathbf{p}} = (c_{\mathbf{p}\uparrow}, c_{\mathbf{p}\downarrow}^*)^T$, the Hamiltonian $H = H_0 + H_{\text{em}} + H_i$. The first part $H_0 \equiv \int \frac{d^3p}{(2\pi)^3} \Psi_{\mathbf{p}}^\dagger \mathbf{g}_{\mathbf{p}} \cdot \boldsymbol{\tau} \Psi_{\mathbf{p}}$, where $\mathbf{g}_{\mathbf{p}} = (\text{Re } \Delta_{\mathbf{p}}, -\text{Im } \Delta_{\mathbf{p}}, \epsilon_{\mathbf{p}} = \frac{p^2}{2m_c} - \epsilon_F)$, $\boldsymbol{\tau} = (\tau_1, \tau_2, \tau_3)$ is the Pauli matrix in the Nambu space, and $\Delta_{\mathbf{p}} = |\Delta|(\hat{p}_x + i\hat{p}_y)$ is the momentum dependent part of a chiral p -wave gap function with $\hat{\mathbf{p}} = \mathbf{p}/|\mathbf{p}|$. The

second part $H_{\text{em}} = \int \frac{d^3q}{(2\pi)^3} [\mathbf{j}_{\mathbf{q}}^{(p)} + \mathbf{j}_{\mathbf{q}}^{(d)}] \cdot \mathbf{A}_{\mathbf{q}}$ is the electromagnetic interaction with the Fourier forms of the paramagnetic current $\mathbf{j}_{\mathbf{q}}^{(p)} = -e \int \frac{d^3p}{(2\pi)^3} \Psi_{\mathbf{p}}^\dagger \frac{2\mathbf{p}+\mathbf{q}}{2m_e} \Psi_{\mathbf{p}+\mathbf{q}} \equiv -e \int \frac{d^3p}{(2\pi)^3} \Psi_{\mathbf{p}}^\dagger \gamma_{\mathbf{p},\mathbf{p}+\mathbf{q}} \Psi_{\mathbf{p}+\mathbf{q}}$ and the diamagnetic current $\mathbf{j}_{\mathbf{q}}^{(d)} = \frac{e^2}{2m_e} \int \frac{d^3p}{(2\pi)^3} \Psi_{\mathbf{p}}^\dagger \tau_3 \Psi_{\mathbf{p}+\mathbf{q}} \mathbf{A}_{\mathbf{q}}$. The last part $H_i = \nu_i \int \frac{d^3q}{(2\pi)^3} \rho_{i\mathbf{q}} \rho_{-\mathbf{q}}$ is the nonmagnetic impurity scattering with the Fourier components of the quasiparticle density $\rho_{\mathbf{q}} = \int \frac{d^3p}{(2\pi)^3} \Psi_{\mathbf{p}}^\dagger \tau_3 \Psi_{\mathbf{p}+\mathbf{q}}$ and impurity density $\rho_{i\mathbf{q}} = \sum_j e^{i\mathbf{q} \cdot \mathbf{R}_j} (\mathbf{R}_j; \text{impurity site})$. It is assumed that the scattering potential is short ranged, and the s -wave channel is dominant.

Let $\pi_{ij}^R(\omega)$ denote the Fourier component of the two-point retarded correlation of the paramagnetic current $\mathbf{j}_{\mathbf{q} \rightarrow 0}^{(p)}$. The Hall conductivity is obtained by the Kubo formula as¹¹ $\sigma_{xy}^{(v)}(\omega) = \pi_{xy}^R(\omega) / i\omega = \sum_{ij} \epsilon_{ij} \pi_{ij}^R(\omega) / 2i\omega$, where ϵ_{ij} is the totally antisymmetric tensor in the 2D plane. To obtain $\sum_{ij} \epsilon_{ij} \pi_{ij}^R(\omega)$, we calculate the Matsubara form $\sum_{ij} \epsilon_{ij} \pi_{ij}(i\omega_n)$ —where $\omega_n = 2n\pi T$ is the bosonic Matsubara frequency at temperature T —and use the relation $\sum_{ij} \epsilon_{ij} \pi_{ij}^R(\omega) = \sum_{ij} \epsilon_{ij} \pi_{ij}(i\omega_n \rightarrow \omega + i\gamma)$, where γ denotes dissipation.¹¹ The Matsubara Green's function for quasiparticles is given by

$$G_{\mathbf{p}}(i\epsilon_m) = \frac{1}{i\epsilon_m + \mathbf{g}_{\mathbf{p}} \cdot \boldsymbol{\tau}} \equiv \begin{bmatrix} \mathcal{G}_{\mathbf{p}}(i\epsilon_m) & \mathcal{F}_{\mathbf{p}}(i\epsilon_m) \\ \mathcal{F}_{\mathbf{p}}^*(-i\epsilon_m) & -\mathcal{G}_{\mathbf{p}}(-i\epsilon_m) \end{bmatrix},$$

where $\epsilon_m = (2m+1)\pi T$.

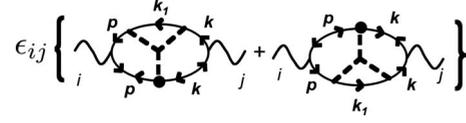


FIG. 1. Leading diagrams of $\sum_{ij} \epsilon_{ij} \pi_{ij}(i\omega_n)$. The lines with the arrows \rightarrow , \leftarrow , and $\rightarrow\leftarrow$ denote quasiparticle Green's functions $\mathcal{G}_{\mathbf{p}}(i\epsilon_m)$, $\mathcal{F}_{\mathbf{p}}(i\epsilon_m)$, and $\mathcal{F}_{\mathbf{p}}^*(i\epsilon_m)$, respectively, in $G_{\mathbf{p}}(i\epsilon_m)$. The lower lines have frequency $\epsilon_{m+n} = \epsilon_m + \omega_n$, while the upper lines have ϵ_m . The dashed lines denote the impurity coupling ν_i . The scattering at the black dots yields the factor $\text{Tr}(\tau_3 \mathbf{g}_{\mathbf{p}} \cdot \boldsymbol{\tau} \mathbf{g}_{\mathbf{k}} \cdot \boldsymbol{\tau})$ in Eq. (3).

In literature,^{12–16} it has been pointed out that there is no contribution of the one-loop diagram to the Matsubara form $\sum_{ij} \epsilon_{ij} \pi_{ij}(i\omega_n)$, i.e., the zeroth-order term of the impurity scattering since $\gamma_{i,\mathbf{p},\mathbf{p}} = p_i/m_e$. Then, vertex corrections must be taken into account to obtain nonzero contributions. The leading contribution is shown in Fig. 1, which is in the first order of the impurity concentration n_i and in the third order of the impurity strength ν_i . These diagrams are similar to the skew scattering diagrams in the extrinsic anomalous Hall effect.¹⁷ We obtain

$$\begin{aligned} \sum_{ij} \epsilon_{ij} \pi_{ij}(i\omega_n) &= n_i \nu_i^3 e^2 \frac{T}{V^3} \sum_{m\mathbf{p}\mathbf{k}\mathbf{k}_1} \sum_{ij} \frac{\epsilon_{ij}}{2} \{ \text{Tr} [G_{\mathbf{p}}(i\epsilon_m) \gamma_{i,\mathbf{p},\mathbf{p}} G_{\mathbf{p}}(i\epsilon_{m+n}) \tau_3 G_{\mathbf{k}}(i\epsilon_{m+n}) \gamma_{j,\mathbf{k},\mathbf{k}} G_{\mathbf{k}}(i\epsilon_m) \tau_3 G_{\mathbf{k}_1}(i\epsilon_m) \tau_3] \\ &\quad + \text{Tr} [G_{\mathbf{p}}(i\epsilon_m) \gamma_{i,\mathbf{p},\mathbf{p}} G_{\mathbf{p}}(i\epsilon_{m+n}) \tau_3 G_{\mathbf{k}_1}(i\epsilon_{m+n}) \tau_3 G_{\mathbf{k}}(i\epsilon_{m+n}) \gamma_{j,\mathbf{k},\mathbf{k}} G_{\mathbf{k}}(i\epsilon_m) \tau_3] \} + \mathcal{O}(n_i \nu_i^4) \\ &= \frac{T}{V^3} \sum_{m\mathbf{p}\mathbf{k}\mathbf{k}_1} \frac{n_i \nu_i^3 e^2 v_F^2 \hat{\mathbf{p}} \times \hat{\mathbf{k}} \text{Tr}(\tau_3 \mathbf{g}_{\mathbf{p}} \cdot \boldsymbol{\tau} \mathbf{g}_{\mathbf{k}} \cdot \boldsymbol{\tau}) \omega_n (\epsilon_m + \epsilon_{m+n})^2 (\epsilon_m \epsilon_{m+n} - E_{\mathbf{k}_1}^2)}{(\epsilon_m^2 + E_{\mathbf{p}}^2)(\epsilon_{m+n}^2 + E_{\mathbf{p}}^2)(\epsilon_m^2 + E_{\mathbf{k}}^2)(\epsilon_{m+n}^2 + E_{\mathbf{k}}^2)(\epsilon_m^2 + E_{\mathbf{k}_1}^2)(\epsilon_{m+n}^2 + E_{\mathbf{k}_1}^2)} + \mathcal{O}(n_i \nu_i^4), \end{aligned} \quad (3)$$

where $E_{\mathbf{p}} = |\mathbf{g}_{\mathbf{p}}| = \sqrt{\epsilon_{\mathbf{p}}^2 + |\Delta_{\mathbf{p}}|^2}$ and $\epsilon_{m+n} \equiv \epsilon_m + \omega_n$. We use the cylindrical coordinate for representing momentum integration. As observed from the leading term of Eq. (3), an azimuthal dependence $\hat{\mathbf{p}} \times \hat{\mathbf{k}} = \sin \theta_{\mathbf{p}\mathbf{k}}$ ($\theta_{\mathbf{p}\mathbf{k}}$: angle between \mathbf{p} and \mathbf{k}) arises from the contraction of the vertex part $\sum_{ij} \epsilon_{ij} \gamma_{i,\mathbf{p},\mathbf{p}} \gamma_{j,\mathbf{k},\mathbf{k}}$ and

$$\text{Tr}(\tau_3 \mathbf{g}_{\mathbf{p}} \cdot \boldsymbol{\tau} \mathbf{g}_{\mathbf{k}} \cdot \boldsymbol{\tau}) = -2i [\text{Re} \Delta_{\mathbf{p}} \text{Im} \Delta_{\mathbf{k}} - (\mathbf{p} \leftrightarrow \mathbf{k})] \quad (4)$$

arises from the impurity scattering at the black dots in Fig. 1. In the chiral p -wave ($p_x + ip_y$ -wave) state, $\text{Tr}(\tau_3 \mathbf{g}_{\mathbf{p}} \cdot \boldsymbol{\tau} \mathbf{g}_{\mathbf{k}} \cdot \boldsymbol{\tau}) = 2i|\Delta|^2 \sin \theta_{\mathbf{p}\mathbf{k}}$. Then, the leading term of Eq. (3) survives after the azimuthal integration. It is obvious that this term yields the second-order contribution of the gap amplitude $|\Delta(T)|^2 \sim |\Delta(0)|^2 (1 - T/T_c)$ in the Ginzburg-Landau (GL) regime. By using GL expansion, we estimate the large ω_n part of the term to perform momentum integral first and Matsubara sum later. By using analytic continuation and the Kubo formula, we obtain

$$\sigma_{xy}^{(v)}(\omega) = \gamma_{\text{BCS}}^2 \left(1 - \frac{T}{T_c}\right) \frac{l_i}{\xi_0} \left(\frac{\epsilon_F}{\pi \tau_0}\right)^{3/2} \frac{\sigma_{xy}^{(0)}}{(\omega + i/\tau_0)^3}, \quad (5)$$

where $\sigma_{xy}^{(0)} = e^2/2\pi d$ (d is the layer distance), $l_i = (n_i d)^{-1/2}$, $\tau_0^{-1} = n_i \nu_i^2 N(0)/2$ [$N(0) = m/2\pi d$ is the density of states at the Fermi surface per spin], $\xi_0 = v_F/\pi T_c$ is the superconducting coherence length at $T=0$, ϵ_F is the Fermi energy, and $\gamma_{\text{BCS}} = |\Delta(0)|/T_c \approx 1.8$.

In general, when we consider chiral states with $l_z = \pm 1, \pm 2, \dots$ —i.e., $(p_x + ip_y)^{l_z}$ -wave states—Eq. (4) becomes $2i|\Delta|^2 \sin l_z \theta_{\mathbf{p}\mathbf{k}}$ and then the leading term of Eq. (3) vanishes after the azimuthal integration—except for $l_z = \pm 1$, i.e., the chiral p -wave state. If we consider chiral states with a horizontal line node such as $(p_x + ip_y)^{l_z} p_z$, Eq. (4) becomes $2i|\Delta|^2 p_z k_z \sin l_z \theta_{\mathbf{p}\mathbf{k}}$ and the leading term also vanishes for any l_z after integrating out the z component of the momentums. For nonchiral ($l_z=0$) and time-reversal breaking states—i.e., $d+is$ -wave pairing—Eq. (4) is proportional to $\cos 2\theta_{\mathbf{p}} - \cos 2\theta_{\mathbf{k}}$ and the leading term will vanish after the

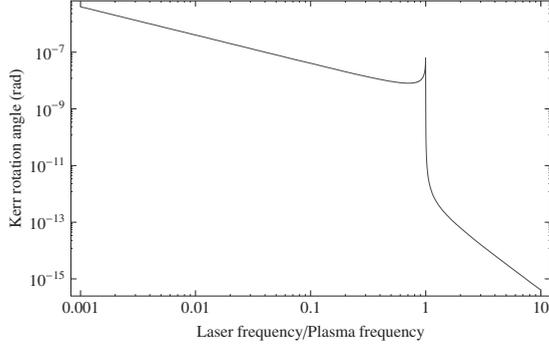


FIG. 2. ω dependence of θ_K in Eq. (2) at $T/T_c=0.8$, obtained using parameters $d=6.8$ Å, $l_i=10000$ Å, $\xi_0=660$ Å, $\omega_p=1.3$ eV, $\epsilon_F=0.14$ eV, and $\tau_0^{-1}=6.6 \times 10^{-5}$ eV (Ref. 3). It is assumed that the cut-off energy of the pairing interaction $\omega_D > 10\omega_p$.

azimuthal integration. For nonchiral and time-reversal symmetric states (s wave, $d_{x^2-y^2}$ wave, ...), $\sigma_{xy}^{(v)}(\omega)$ should be zero because of the symmetrical reason. In fact, it is easy to confirm that Eq. (4) becomes zero since the gap function can be made real for these states by using the $U(1)$ phase transformation of fermion fields. To sum up, in this impurity scattering mechanism, $\sigma_{xy}^{(v)}(\omega)$ is suppressed or is zero for any state other than the chiral p -wave state (see Ref. 6).

The diagonal component $\sigma_{xx}^{(v)}(\omega)$ is effectively approximated by the Drude form $\sigma_{xx}^{(v)}(\omega) \approx \omega_p^2 \tau_0 (1 - i\omega\tau_0)^{-1}$ in the high-frequency limit $\omega \gg 2|\Delta|$,¹⁸ where $\omega_p = \sqrt{n_e e^2 / m_e}$ is the plasma frequency and n_e is the electron number density. In fact, this behavior of $\sigma_{xx}^{(v)}(\omega)$ has been verified experimentally in the superconducting state of Sr_2RuO_4 .¹⁹

Let us estimate θ_K from Eq. (2). We use suitable parameters for the experiment, i.e., $d=6.8$ Å, $\xi_0=660$ Å, $\omega=0.8$ eV, $\omega_p=1.3$ eV, $\epsilon_F=0.14$ eV, and $\tau_0^{-1}=6.6 \times 10^{-5}$ eV.³ The impurity mean distance l_i is rather ambiguous, and we consider a variation 1000–5000 Å.²⁰ The estimated value of θ_K from Eq. (2) at $T/T_c=0.8$ is 6 nrad for $l_i=1000$ Å and 30 nrad for $l_i=5000$ Å. The latter case agrees well with the measurement result of approximately 60 nrad at the same temperature.³

The frequency dependence of θ_K in Eq. (2) at $T/T_c=0.8$ is plotted in Fig. 2. We find that θ_K behaves as ω^{-1} for $\omega < \omega_p$, as indicated by Eqs. (5) and (6). At $\omega=\omega_p$, θ_K shows a sharp peak and behaves as ω^{-3} for $\omega > \omega_p$.

The temperature dependence of θ_K can be explained as follows: Equation (2) is effectively approximated by

$$\theta_K \approx \frac{\omega^2}{\omega_p^3} \text{Re}[\sigma_{xy}^{(v)}(\omega)], \quad (6)$$

when $\omega_p^2 - \omega^2 \gg |\omega\sigma^{(v)}(\omega)|$ and $\omega\tau_0 \gg 1$ (these conditions are satisfied using suitable parameters in the experiment). The approximated form Eq. (6) indicates that θ_K depends linearly on the temperature in the GL region [see also Eq. (5)]. This result is not in agreement with the experimental report;³ however, the error bars of the data are large and it appears that the temperature dependence is difficult to discuss.

The obtained result might be overestimated since it is assumed that every scatterer has the same fixed potential

strength rather than a distribution. We also suppose that the energy scale of the pairing interaction ω_D is well above the laser frequency $\omega \approx 0.8$ eV. Although the nature of the pairing interaction is not elucidated, ω_D is likely to be less than the used laser frequency. It is pointed out that the Hall conductivity would be suppressed for $\omega > \omega_D$.⁵ However, we believe that the presented mechanism plays an important role in the PKE in Sr_2RuO_4 .³

We comment on previously proposed theories of the PKE in the chiral p -wave state. In Ref. 21, $\sigma_{xy}^{(s)}$ in Eq. (1) is obtained using the relation $\sigma_{xy}^{(s)}(\omega) = \frac{i}{2} \epsilon_{ij} \frac{\partial}{\partial q_i} \pi_{0j}^R(\omega, \mathbf{q})|_{\mathbf{q}=0}$, where $\pi_{0j}^R(\omega, \mathbf{q})$ is the correlation between charge and current densities. The calculation has been performed in the case without any impurity, and nonzero values of $\sigma_{xy}^{(s)}$ have been obtained. However, as shown in Eq. (2), $\sigma_{xy}^{(v)}(\omega)$ and not $\sigma_{xy}^{(s)}(\omega)$ is responsible for the PKE. In Ref. 21, it is implicitly assumed that $\sigma_{xy}^{(s)}(\omega) = \sigma_{xy}^{(v)}(\omega)$ in the high-frequency limit [see the discussion below Eq. (17) in Ref. 21]. (The same assumption has been made in Ref. 22.) However, this would not be true since $\sigma_{xy}^{(v)}(\omega)$ is zero without impurity scattering for an arbitrary frequency.^{12–15} This problem has also been pointed out in recent arguments.^{4,5} In Refs. 4 and 5, $\sigma_{xy}^{(s)}(\omega, \mathbf{q})$ has been discussed. A remarkable finding is that the finite \mathbf{q} effect is responsible for the PKE (a similar argument has been provided in Ref. 23); however, the obtained Kerr angle is about 9 orders of magnitude smaller than that obtained experimentally.^{4,5}

Let us turn to discuss the Chern-Simons term $\epsilon_{\mu\rho\nu} A_\mu \partial_\rho A_\nu$ ($\mu, \rho, \nu=0, 1, 2$), which is generally induced in the low-energy and long-wavelength effective Lagrangian for gauge fields obtained by integrating out 2D electrons in a system with parity and time-reversal symmetry breakings.²⁴ The origin of the term is closely related to the parity anomaly.^{25–28} It has been pointed out that for the chiral p -wave superconductor, a nonzero value of $\sigma_{xy}^{(s)}(\omega=\mathbf{q}=0)$ is obtained without impurity scattering. At $T=0$, $\sigma_{xy}^{(s)}(0) = \frac{e^2}{4\pi}$.^{12–15} The finite-temperature effect was investigated in the GL scheme^{15,29} (see also Ref. 16). This indicates that a part of the Chern-Simons term $\frac{\sigma_{xy}^{(s)}(0)}{2} \epsilon_{ij} (A_0 \partial_i A_j + A_i \partial_j A_0)$ is induced in the effective Lagrangian.^{12,13} We can conclude that this part has an “intrinsic” origin since it is induced without impurity scattering while $\sigma_{xy}^{(v)}(0)=0$, and the other part of the Chern-Simons term $\epsilon_{ij} A_i \partial_0 A_j$ is not induced.^{12–15} As we have emphasized, $\sigma_{xy}^{(v)}(\omega)$ becomes nonzero when we take into account vertex corrections from impurities, shown in Fig. 1. From the leading term of Eq. (3), we can observe that in the static limit the second-order contributions of the gap amplitude vanish occasionally and the fourth-order contributions give

$$\sigma_{xy}^{(v)}(0) = \sigma_{xy}^{(0)} \frac{127\zeta(7)}{128\pi^4} \frac{l_i}{\xi_0} \left(\frac{\epsilon_F}{\pi\tau_0 T_c} \right)^{3/2} \left(1 - \frac{T}{T_c} \right)^2 \gamma_{\text{BCS}}^4,$$

near T_c . This indicates that the other part $\frac{\sigma_{xy}^{(s)}(0)}{2} \epsilon_{ij} A_i \partial_0 A_j$ has an “extrinsic” origin.

In summary, we have discussed the PKE in a chiral p -wave superconductor. We have estimated the contribution of impurity scattering in the chiral p -wave condensate. The

skew-scattering-type diagrams (see Fig. 1) show the leading contribution. In this impurity-induced mechanism, the PKE would be suppressed or would be zero for any state other than the chiral p -wave state (the possibility of nonunitary pairing is not taken into account, see Ref. 6).

The author is grateful to D. S. Hirashima, H. Kontani, Y. Maeno, and V. M. Yakovenko for the useful discussions and comments. This work was supported by Grant in Aid for Scientific Research (Grant No. 19740241) from the Ministry of Education, Culture, Sports, Science, and Technology.

*jungoryo@s.phys.nagoya-u.ac.jp

- ¹For a review, see, A. P. Mackenzie and Y. Maeno, *Rev. Mod. Phys.* **75**, 657 (2003).
- ²R. M. White and T. H. Geballe, *Long Range Order in Solids* (Academic, New York, 1979), pp. 317–321.
- ³J. Xia, Y. Maeno, P. T. Beyersdorf, M. M. Fejer, and A. Kapitulnik, *Phys. Rev. Lett.* **97**, 167002 (2006).
- ⁴R. M. Lutchyn, P. Nagornykh, and V. M. Yakovenko, *Phys. Rev. B* **77**, 144516 (2008).
- ⁵R. Roy and C. Kallin, *Phys. Rev. B* **77**, 174513 (2008).
- ⁶The PKE would occur in the nonunitary (spin-polarized) pairing state; (Ref. 7), however, this state is not taken into account here since it is difficult to imagine that such a state arises at zero field without some special condition, for example, the superconducting phase is surrounded by a ferromagnetic phase. Sr_2RuO_4 does not have a ferromagnetic phase.
- ⁷For a review, see, M. Sigrist and K. Ueda, *Rev. Mod. Phys.* **63**, 239 (1991), and references therein.
- ⁸P. N. Argyres, *Phys. Rev.* **97**, 334 (1955).
- ⁹X. G. Wen and A. Zee, *Phys. Rev. Lett.* **62**, 2873 (1989); *Phys. Rev. B* **43**, 5595 (1991).
- ¹⁰In Eq. (1), the unitarity gauge is used, which eliminates the phase of the gap function (see S. Weinberg, *The Quantum Theory of Fields* (Cambridge University Press, Cambridge, England, 1996), Vol. II). Even in the case that $\sigma_{xy}^{(v)} \neq \sigma_{xy}^{(s)}$, the gauge symmetry in Eq. (1) will be restored when the phase mode is taken into account explicitly (Refs. 12 and 13).
- ¹¹G. D. Mahan, *Many-Particle Physics*, 3rd ed. (Kluwer, New York, 2000).
- ¹²G. E. Volovik, *Sov. Phys. JETP* **67**, 1804 (1988).
- ¹³J. Goryo and K. Isihikawa, *Phys. Lett. A* **246**, 549 (1998); **260**, 294 (1999).
- ¹⁴N. Read and D. Green, *Phys. Rev. B* **61**, 10267 (2000).
- ¹⁵A. Furusaki, M. Matsumoto, and M. Sigrist, *Phys. Rev. B* **64**, 054514 (2001).
- ¹⁶B. Horovitz and A. Golub, *Europhys. Lett.* **57**, 892 (2002).
- ¹⁷J. Smit, *Physica (Amsterdam)* **24**, 39 (1958).
- ¹⁸D. C. Mattis and J. Bardeen, *Phys. Rev.* **111**, 412 (1958).
- ¹⁹T. Katsufuji, M. Kasai, and Y. Tokura, *Phys. Rev. Lett.* **76**, 126 (1996).
- ²⁰Y. Maeno (private communication).
- ²¹V. M. Yakovenko, *Phys. Rev. Lett.* **98**, 087003 (2007).
- ²²V. P. Mineev, *Phys. Rev. B* **76**, 212501 (2007); **77**, 180512(R) (2008).
- ²³J. Goryo and K. Ishikawa, *J. Phys. Soc. Jpn.* **67**, 3006 (1998).
- ²⁴S. Deser, R. Jackiw, and S. Templeton, *Phys. Rev. Lett.* **48**, 975 (1982).
- ²⁵A. J. Niemi and G. W. Semenoff, *Phys. Rev. Lett.* **51**, 2077 (1983).
- ²⁶A. N. Redlich, *Phys. Rev. Lett.* **52**, 18 (1984).
- ²⁷K. Ishikawa, *Phys. Rev. Lett.* **53**, 1615 (1984); *Phys. Rev. D* **31**, 1432 (1985).
- ²⁸F. D. M. Haldane, *Phys. Rev. Lett.* **61**, 2015 (1988).
- ²⁹J. Goryo and M. Sigrist, *J. Phys.: Condens. Matter* **12**, L599 (2000).